

Specific heat at the transition in a superconductor with fluctuating magnetic moments

Šimon Kos and Ivar Martin

Theoretical Division, Los Alamos National Laboratory, Los Alamos, NM 87545

C.M. Varma

Bell laboratories, Murray Hill, NJ 07974

In the heavy-fermion materials CeCoIn₅ and UBe₁₃, the superconducting order parameter is coupled to fluctuating magnetization of the uncompensated part of the localized f -moments. We find that this coupling decreases the superconducting transition temperature and increases the jump of the specific-heat coefficient, which indicates entropy transfer from the magnetic to the superconducting degree of freedom at the transition temperature. Below the transition, we find that the magnetic fluctuations are suppressed. We discuss the relation of our results to experiments on CeCoIn₅ under pressure.

In this paper, we examine the effects of *fluctuating* paramagnetic moments on the specific-heat jump at the transition ΔC . We are motivated to examine this question due to recent experiments in CeCoIn₅, a heavy-fermion superconductor with an unusually large ratio of $\Delta C/\gamma T_c \approx 5$ at ambient pressure,¹ whereas the BCS value for singlet s -wave superconductor is 1.43. Anisotropy of the gap further decreases this value; for instance, for a d -wave or an anisotropic p -wave superconductor, it is suppressed by factors 2/3 or 5/6, respectively. We also recall that UBe₁₃², one of the first heavy Fermion superconductors to be discovered, has $\Delta C/\gamma T_c \approx 2$. In UBe₁₃, the normal-state specific-heat coefficient γ above T_c increases as temperature is lowered indicating that the asymptotic Fermi-liquid state is not reached down to T_c . In CeCoIn₅, the integrated measured entropy

$$\int_0^{T_c} C/T dT \quad (1)$$

is about 3 times larger than $\gamma(T_c)T_c$ ¹ assuring that were it not for the superconducting instability, a further enhancement of the normal state specific heat at lower temperatures would occur. Indeed, in a magnetic field just above $H_{c2} = 5\text{T}$, the specific-heat coefficient has a sharp upturn around 1K as T decreases below T_c and continues to rise down to the lowest measured temperature 0.2K. The entropy is quite adequately balanced between this measurement and the zero-field entropy of the superconducting state demonstrating the consistency of the experimental measurements. We may associate the high temperature constant γ state to an unstable Fermi-liquid state characterized by a Fermi temperature $T_{Fh} \approx 35 - 50\text{K}$ (see (10) below), and the low temperature constant γ state to an asymptotically stable Fermi-liquid state characterized by a temperature T_{Fl} . The measurement of γ above 5T suggests that $T_{Fl} \simeq 1\text{K}$. Thus, $T_{Fh} \gg T_c$. We see that T_c is bigger than T_{Fl} by a factor 2 or 3. To simplify the analysis, we shall assume $T_c \gg T_{Fl}$. We shall see that the results still give a good agreement with the experimental data.

The two energy scales can originate in heavy fermions from a variety of causes. For example, multistage Kondo effects can arise in magnetic impurities when crystal field splittings are taken into account³; the values of the crystal-field splittings have been measured in various experiments^{4,5}. In fact, a low Kondo temperature scale of about 1.5K has been deduced⁵ from the crystal-field scheme and the high Kondo temperature of 35K. A suppressed putative antiferromagnetic transition below T_c could also provide a lower energy scale. Such a transition would of course also be suppressed in a field as large as 5 Tesla required to suppress superconductivity and the $\gamma(T)$ would then show a rise as observed below about 1 K (followed by a decline). In a recent detailed analysis⁶, the specific-heat and magnetic-susceptibility data of CeCoIn₅ have been decomposed into a contribution from a heavy Fermi liquid characterized by T_{Fh} and a contribution from local impurities with Kondo temperature T_{Fl} . The microscopic origin of the scale T_{Fl} is not important in our model and the ensuing calculations.

We shall study the renormalizations of the specific heat (and magnetic fluctuations) using the following Ginzburg-Landau free energy function.

$$\begin{aligned} \mathcal{F}[\psi, \mathbf{M}(\mathbf{r})] &= \int_V d^d r \left[\frac{a(T - T_c)}{2} |\psi|^2 + \frac{b}{4} |\psi|^4 + \frac{\alpha(T + T_{sf})}{2} \mathbf{M}^2(\mathbf{r}) + \frac{\eta}{2} |\psi|^2 \mathbf{M}^2(\mathbf{r}) \right] \\ &= V \left[\frac{a(T - T_c)}{2} |\psi|^2 + \frac{b}{4} |\psi|^4 \right] + \frac{1}{2V} \sum_{\mathbf{k}}^{k_c} (\alpha(T + T_{sf}) + \eta |\psi|^2) \mathbf{M}_{\mathbf{k}}^2. \end{aligned} \quad (2)$$

In (2), ψ is the superconductivity order parameter, $\mathbf{M}(\mathbf{r})$ is the magnetization at $\mathbf{r}$ and the coupling η between the superconducting order parameter ψ and the magnetization $\mathbf{M}(\mathbf{r})$ is of the lowest allowed order and is independent of

momentum and frequency. The magnetic fluctuations are assumed to be local and classical:

$$\chi_0(T) = \frac{1}{\alpha(T + T_{sf})}, \quad (3)$$

The assumptions underlying the free energy (2) are the following: The fluctuations characteristic of the high temperature renormalized Fermi energy T_{Fh} are assumed to lead to pairing and to determine T_c and the bare parameters a and b in Eq. (2). The fluctuations characteristic of the low temperature Fermi energy T_{Fl} have a characteristic energy $T_{sf} = \mathcal{O}(T_{Fl})$. As stated above, we further assume $T_{Fh} \gg T_c \gg T_{Fl}$ for CeCoIn₅. Two simplifications follow from this which are used in (2): (i) The magnetic fluctuations characterised by T_{sf} can be treated classically near T_c , (ii) there is clear separation in the microscopic processes leading to T_c, a, b on the one hand and those parametrized in η . Note that the term involving η correctly describes the Abrikosov-Gorkov⁷ effects of magnetic impurities on superconductivity to leading order.

We can obtain the renormalized superconducting transition temperature, the jump of the specific-heat coefficient, and the susceptibility from the Helmholtz free energy. To calculate the Helmholtz free energy, we must integrate over all possible configurations of $\mathbf{M}$ and ψ . We shall do this in a two-step process. First we integrate over $\mathbf{M}$, because the integral is Gaussian, and can therefore be done exactly. That gives us a contribution $\mathcal{F}_{fluct}(|\psi|^2)$ to the superconducting Ginzburg-Landau free energy. We then approximate the integral over ψ by the value of the integrand at its maximum.

$$\begin{aligned} \exp - \frac{\mathcal{F}_{fluct}(|\psi|^2)}{T} &= \int \mathcal{D}\mathbf{M}_{\mathbf{k}} \exp - \frac{1}{TV} \sum_{\mathbf{k}}^{k_c} \frac{1}{2} (\alpha(T + T_{sf}) + \eta(k)|\psi|^2) |\mathbf{M}_{\mathbf{k}}|^2 \\ &= \prod_{\mathbf{k}}^{k_c} \left(\frac{\pi}{\frac{\alpha(T + T_{sf}) + \eta(k)|\psi|^2}{2TV}} \right)^{3/2} \end{aligned} \quad (4)$$

so

$$\frac{\mathcal{F}_{fluct}(|\psi|^2)}{T} = \frac{\mathcal{F}_0}{T} + \frac{3}{2} \frac{VT}{l^d} \left[\frac{\eta}{\alpha(T + T_{sf})} |\psi|^2 - \frac{1}{2} \left(\frac{\eta}{\alpha(T + T_{sf})} \right)^2 |\psi|^4 \right] + \mathcal{O}(|\psi|^6). \quad (5)$$

Here

$$\mathcal{F}_0 = \frac{3}{2} VT \int \frac{d^d k}{(2\pi)^d} \ln \frac{\alpha(T + T_{sf})}{2\pi TV} \quad (6)$$

is the free energy of the uncoupled magnetic fluctuations, and l is the lattice constant. This formula is correct in the classical regime of the magnetic fluctuations, $T_{Fl} \ll T$ that we are studying here. In the quantum regime, that is, when the temperature is lower than the energy of the magnetic mode at momentum k_c , we have to cut off the momentum integration at the value corresponding to T .

The Ginzburg-Landau energy density for the superconducting order parameter after including the effect of the fluctuating magnetization is

$$F_{sc}(|\psi|^2) = \frac{a}{2} \left(T - T_c + T_{\psi M} \frac{T}{T + T_{sf}} \right) |\psi|^2 + \frac{b}{4} \left(1 - T_{\psi M}^2 l^d \frac{a^2}{3b} \frac{T}{(T + T_{sf})^2} \right) |\psi|^4. \quad (7)$$

Here we have combined η and α into one parameter with the dimension of temperature

$$T_{\psi M} \equiv \frac{3\eta}{l^d a \alpha}, \quad (8)$$

which characterizes the strength of the magnetic fluctuations. From the functional (2), we see that

$$\Delta\gamma \equiv l^d \frac{a^2}{2b} \quad (9)$$

is the jump of the specific heat coefficient at T_c of the bare superconductor per unit cell, so it has dimension of inverse temperature. Its value T_γ is of the order T_{Fh} . From the experimental values of $\gamma(T > T_c) \simeq 0.2 - 0.3 J/molK^2$ using $R \simeq 8 J/molK$, we obtain

$$T_\gamma \simeq T_{Fh} = 35 - 50 K. \quad (10)$$

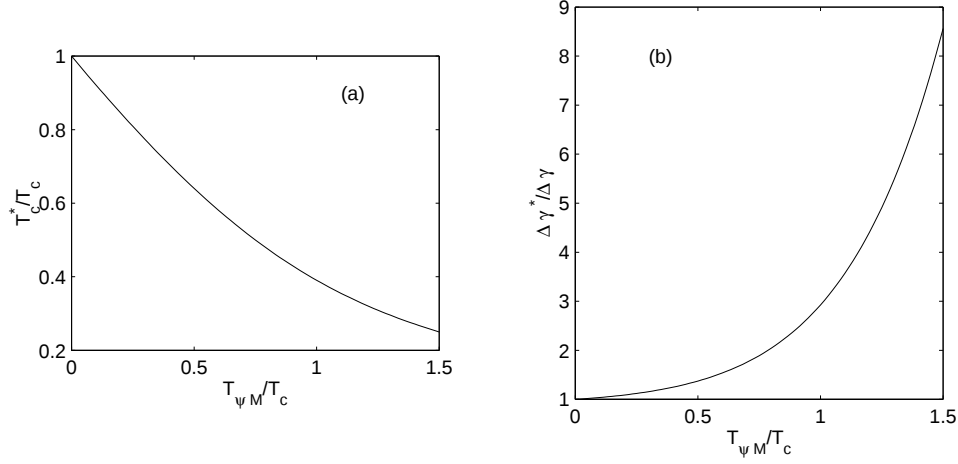


FIG. 1: (a) Renormalized transition temperature and (b) renormalized jump of the specific-heat coefficient as a function of $T_{\psi M}$.

Once T_γ is more than an order of magnitude bigger than the transition temperature, the measurable quantities are not very sensitive to its precise value. Behavior of F_{sc} close to zero defines the renormalized Ginsburg-Landau parameters

$$F_{sc}(|\psi|^2) \simeq \frac{a^*}{2}(T - T_c^*)|\psi|^2 + \frac{b^*}{4}|\psi|^4. \quad (11)$$

The new transition temperature T_c^* satisfies the equation

$$\delta T_c \equiv T_c^* - T_c = -T_{\psi M} \frac{T_c^*}{(T_c^* + T_{sf})}, \quad (12)$$

and the new specific heat jump is given by

$$\frac{\Delta\gamma^*}{\Delta\gamma} = \frac{\left(1 + \frac{T_{\psi M} T_{sf}}{(T_c^* + T_{sf})^2}\right)^2}{1 - \frac{T_{\psi M}^2}{T_\gamma} \frac{T_c^*}{(T_c^* + T_{sf})^2}}. \quad (13)$$

We note that the coupling to the magnetic fluctuations decreases the transition temperature and increases the specific-heat jump. We would like to compare our results to the experiments on CeCoIn₅ under pressure⁸, which show, that applying pressure increases T_c and decreases the jump of the specific-heat coefficient. In the first approximation, we will assume that the bare superconducting parameters a , b , and T_c , as well as the bare magnetic parameters α and T_{sf} are set at high energies, and thus do not change with pressure. The pressure is expected to change only the low-energy coupling η and hence the temperature $T_{\psi M}$. In Fig.1, we plot the dimensionless quantities T_c^*/T_c and $\Delta\gamma^*/\Delta\gamma$ as functions of the dimensionless variable $T_{\psi M}/T_c$, to show that T_c^* decreases and $\Delta\gamma^*$ increases as $T_{\psi M}$ increases. Hence, our interpretation of the experimental results is that the hydrostatic pressure suppresses $T_{\psi M}$. In Fig.1, we used the values $T_c = 6\text{K}$, $T_{sf} = 1.5\text{K}$ (in agreement with the measurements of γ in the magnetic field¹ discussed in the introduction), and $T_\gamma = 50\text{K}$. Note that $T_{sf} < T_c$, which justifies our assumptions that the fluctuating moments are classical. These values are reasonable on physical grounds, and give a reasonable agreement between the experimental data and the calculated results (12) and (13). Experimentally, as the applied hydrostatic pressure changes from 0 to 1.48 GPa, T_c^* and $\Delta\gamma^*/\Delta\gamma$ change from 2.3 to 2.7K and from 3 down to 2, respectively. The experimental data correspond to $T_{\psi M} \approx T_c$: From the formulas (12) and (13), we find that as $T_{\psi M}/T_c$ changes from 1.05 down to 0.85, T_c^* and $\Delta\gamma^*/\Delta\gamma$ change from 2.2 to 2.7K and from 3.0 down to 2.1, respectively. The fit to the experimental data is, of course, not exact because at each value of the pressure, we are solving two equations (11) and (12) for one unknown $T_{\psi M}$. For a detailed comparison with the experiment, we also need to assume a pressure dependence of another bare parameter, for example T_{sf} , but that pressure dependence comes out much weaker than the pressure dependence of $T_{\psi M}$, in agreement with our considerations at the beginning of this paragraph.

Finally, we calculate the change of the magnetic susceptibility relative to its bare value (3) due to the interaction η to see the effect of superconductivity on magnetic fluctuations. The magnetic susceptibility is given by

$$\chi(T, q) = \frac{\int \mathcal{D}\mathbf{M}_{\mathbf{k}} \mathcal{D}\psi \mathcal{D}\psi^* |\mathbf{M}_{\mathbf{q}}|^2 e^{-\frac{\mathcal{F}[\psi, \mathbf{M}]}{T}}}{\int \mathcal{D}\mathbf{M}_{\mathbf{k}} \mathcal{D}\psi \mathcal{D}\psi^* e^{-\frac{\mathcal{F}[\psi, \mathbf{M}]}{T}}}; \quad (14)$$

we do both integrals by the two-step process described earlier. Above T_c^* , $\psi = 0$, so the susceptibility stays equal to (3). Below T_c^* , the $\mathbf{M}$ integral gives

$$\int \mathcal{D}\mathbf{M}_{\mathbf{k}} |\mathbf{M}_{\mathbf{q}}|^2 e^{-\frac{1}{TV} \sum_{\mathbf{k}}^{k_c} \frac{1}{2} (\alpha(T+T_{sf}) + \eta|\psi|^2) |\mathbf{M}_{\mathbf{k}}|^2} = \frac{1}{2(\alpha(T+T_{sf}) + \eta|\psi|^2)} \prod_{\mathbf{k}}^{k_c} \left(\frac{\pi}{\frac{\alpha(T+T_{sf}) + \eta|\psi|^2}{2TV}} \right)^{3/2}. \quad (15)$$

The extra factor $1/(\alpha(T+T_{sf}) + \eta|\psi|^2)$ on the right-hand side will change the extremum in the numerator of (14) by a number of the order of $1/V$ relative to the denominator, so we will neglect that difference. Then everything but this factor cancels between the numerator and the denominator, and we get

$$\chi(T, q) = \frac{1}{\alpha(T+T_{sf}) + \eta|\psi(T)|^2} \quad (16)$$

with $|\psi(T)|^2$ obtained by minimization of (11). We see that the magnetic fluctuations are suppressed by coupling to superconductivity, but susceptibility of the localized moments remains finite down to zero temperature. Both effects are consistent with measurements of Knight shift⁹.

In conclusion, we propose that the anomalously big specific-heat jump at the superconducting transition in UBe₁₃ and CeCoIn₅ is caused by interaction between superconducting ordering and fluctuating unordered classical magnetic moments of localized f-electrons. We describe such a coupling between the two degrees of freedom by the simplest possible Ginsburg-Landau functional. We find that the transition temperature decreases and the jump of the specific-heat coefficient increases as the strength of the paramagnetic fluctuations and/or of their coupling to the superconducting order parameter increase. Below the transition, magnetic susceptibility is suppressed but remains finite down to zero temperature.

We thank Ar. Abanov, E. Abrahams, N. Curro, M.F. Hundley, E. Lengeyel, D.K. Morr, R. Movshovich, N. Oeschler, and D. Pines for useful discussions. We especially wish to acknowledge the sharing of the data analysis⁶ by S. Nakatsuji.

¹ C. Petrovic *et al.* J. Phys. Condens. Matter. **13**, L337 (2001)

² R.A. Fisher *et al.* in *Theoretical and experimental aspects of valence fluctuations and heavy fermions*, L.C. Gupta and S.K. Malik, eds. (Plenum Press, New York, 1987)

³ P. Nozieres and A. Blandin, J. Phys. (Paris) **41**, 193 (1980).

⁴ N. Curro *et al.*, cond-mat/0205354

⁵ S. Nakatsuji *et al.*, Phys. Rev. Lett. **89**, 106402 (2002).

⁶ S. Nakatsuji, unpublished.

⁷ A.A. Abrikosov, L.P. Gor'kov, JETP **15**, 752 (1962)

⁸ G. Sparn *et al.*, Physica **B 312-313**, 138 (2002).

⁹ N. Curro *et al.* Phys. Rev. **B 64**, 180514 (2001)